

STRUX® 90/40

Synthetic macro fiber reinforcement

ASTM C1116

Product Description

STRUX® 90/40 synthetic macro fiber reinforcement is a unique form of high strength, high modulus synthetic macro reinforcement that is evenly distributed throughout the concrete matrix. STRUX 90/40 adds toughness, impact and fatigue resistance to concrete. Unlike traditional microfiber reinforcement, STRUX 90/40 is specifically engineered to provide high, post-crack control performance. Reinforced concrete with STRUX 90/40 has been shown to reliably achieve average residual strength values in excess of 150 psi (1.0 MPa) at dosages that can easily be batched and finished. It consists of synthetic macro fibers 1.55 in. (40 mm) in length with an aspect ratio of 90 that have specifically been designed to replace welded wire fabric, steel fibers, light rebar and other secondary reinforcement in slab-on-ground flooring, thin-walled precast applications and composite steel floor deck. STRUX 90/40 is a user-friendly fiber reinforcement which is easier and safer to use, compared to these other types of reinforcement.

Uses

Slab-on-Ground

STRUX 90/40 is specially designed for ease of use, rapid dispersion, good finishability and improved pumpability in slab-on-ground flooring

Product Advantages

- Savings from lower labor costs and fewer construction days
- Enhances safety by eliminating handling of steel fibers, welded wire fabrics or light rebar
- Eliminates concerns of proper positioning of reinforcement
- Provides superior crack control due to the geometry and elastic modulus
- Abrasion resistance and will not corrode
- Controls plastic and drying shrinkage cracks

and many precast applications. STRUX 90/40 may be used in commercial floors, industrial floors, residential floors, other flat work applications and form work applications. The addition rate of STRUX 90/40 can be easily calculated using Grace's SDS Software, using several factors such as compressive strength of concrete, modulus of sub-grade reaction, thickness of concrete and applied load. Please consult your Grace sales representative for proper addition rate of STRUX 90/40 for your application. Always consult local building codes (refer to Engineering Bulletin 1).

Composite Steel Floor Deck for Normal and Lightweight Concrete

STRUX 90/40 can be used as a suitable alternative to WWF specified for temperature and shrinkage reinforcement for composite steel floor decks. STRUX 90/40 complies with *American National Standards Institute/Steel Deck Institute* (ANSI/SDI C-1.0) design code provision for minimum reinforcing at minimum addition rate of 4 lbs/yd³ (2.4 kg/m³). STRUX 90/40 is UL (U.S.) and ULC (Canada) classified with fire ratings up to 2 hours for D700, F700, D800, F800, D900 and F900 except 909 at a maximum addition rate of 5 lbs/yd³ (3.0 kg/m³).

Addition Rates

STRUX 90/40 addition rates are dependent on the specific application and desired properties and will vary between 3.0 to 12.0 lbs/yd³ (1.8 to 7.0 kg/m³).

Mix Design

The utilization of STRUX 90/40 may require the use of a superplasticizer such as ADVA® to restore the required workability. In addition, slight increases in fine aggregate contents may be needed.

STRUX 90/40 may be added to concrete at any point during the batching or mixing process. After fiber addition, the concrete must be mixed at the minimum of 70 revolutions to ensure adequate dispersion.

Please contact your Grace representative with any questions. For more detailed instructions refer to Technical Bulletin TB-1200.



STRUX® 90/40 fiber as marketed by W. R. Grace & Co.—Conn. is classified by Underwriters Laboratories Inc. for use as an alternative, or in addition to, the welded wire fabric in 1, 1½ and 2 hr floor-ceiling D700, F700, D800, F800, D900 and F900 (except 909) Series Designs. Fibers to be added to the concrete mix at maximum addition rate of 5 lbs/yd³ (3.0 kg/m³).

Compatibility with Other Admixtures and Batch Sequencing

STRUX 90/40 is compatible with all Grace admixtures. Their action in concrete is mechanical and will not affect the hydration process of the cement or compressive strength. Each liquid admixture should be added separately to the concrete mix.

Packaging

STRUX 90/40 is available in 1.0 lb or 5.0 lb (.5 kg or 2.3 kg) Concrete-Ready™ bags.

STRUX 90/40 Properties

Specific gravity	0.92
Absorption	None
Modulus of elasticity	1,378 ksi (9.5 GPa)
Tensile strength	90 ksi (620 MPa)
Melting point	320°F (160°C)
Ignition point	1,094°F (590°C)
Alkali, acid & salt resistance	High


Flexural Strength and Toughness (Compressive Strength: 4,000 psi) according to ASTM C1609-05

STRUX 90/40 Dosage Rate	Specimen cross-section		Peak Load P_p (lbf)	Peak Strength f_p (psi)	Peak-load deflection δ_p (in.)	Residual loads		Residual strengths		Toughness $T_{150,3.0}$ (lbf-in.)	JCI-SF4 ¹⁾ $f_{e,3}$ (psi)	TR34 ²⁾ $R_{e,3}$ (%)
	Width (in.)	Depth (in.)				$P_{150,0.75}$ (lbf)	$P_{150,3.0}$ (lbf)	$f_{150,0.75}$ (psi)	$f_{150,3.0}$ (psi)			
0.19% (3.0 lbs/yd ³)	6.00	5.95	6,702	565	0.0019	1,299	952	110	80	160	115	20.0%
0.32% (5.0 lbs/yd ³)	6.00	6.00	7,064	595	0.0020	1,905	1,558	160	130	240	165	28.5%
0.50% (7.75 lbs/yd ³)	6.00	5.95	6,860	580	0.0020	2,770	2,251	230	190	330	230	40.5%

Flexural Strength and Toughness (Compressive Strength: 28 MPa) according to ASTM C1609-05

STRUX 90/40 Dosage Rate	Specimen cross-section		Peak Load P_p (N)	Peak Strength f_p (MPa)	Peak-load deflection δ_p (mm)	Residual loads		Residual strengths		Toughness $T_{150,3.0}$ (Joule)	JCI-SF4 ¹⁾ $f_{e,3}$ (MPa)	TR34 ²⁾ $R_{e,3}$ (%)
	Width (mm)	Depth (mm)				$P_{150,0.75}$ (N)	$P_{150,3.0}$ (N)	$f_{150,0.75}$ (MPa)	$f_{150,3.0}$ (MPa)			
0.19% (1.8 kg/m ³)	152	151	29,813	3.90	0.048	5,776	4,236	0.75	0.55	18	0.80	20.0%
0.32% (3.0 kg/m ³)	152	152	31,422	4.10	0.050	8,472	6,932	1.10	0.90	27	1.15	28.5%
0.50% (4.6 kg/m ³)	152	151	30,513	4.00	0.050	12,323	10,012	1.60	1.30	37	1.60	40.5%

1) Japan Concrete Institute (JCI) Standard Test Method for Flexural Strength and Flexural Toughness of Fiber Reinforced Concrete, (Standard SF4), JCI Standards for Test Methods of Fiber Reinforced Concrete, Japan Concrete Institute, 1983. 2) The Concrete Society Technical Report 34 Concrete industrial ground floors—A guide to their design and construction, The Society, Crowthome, 2003.

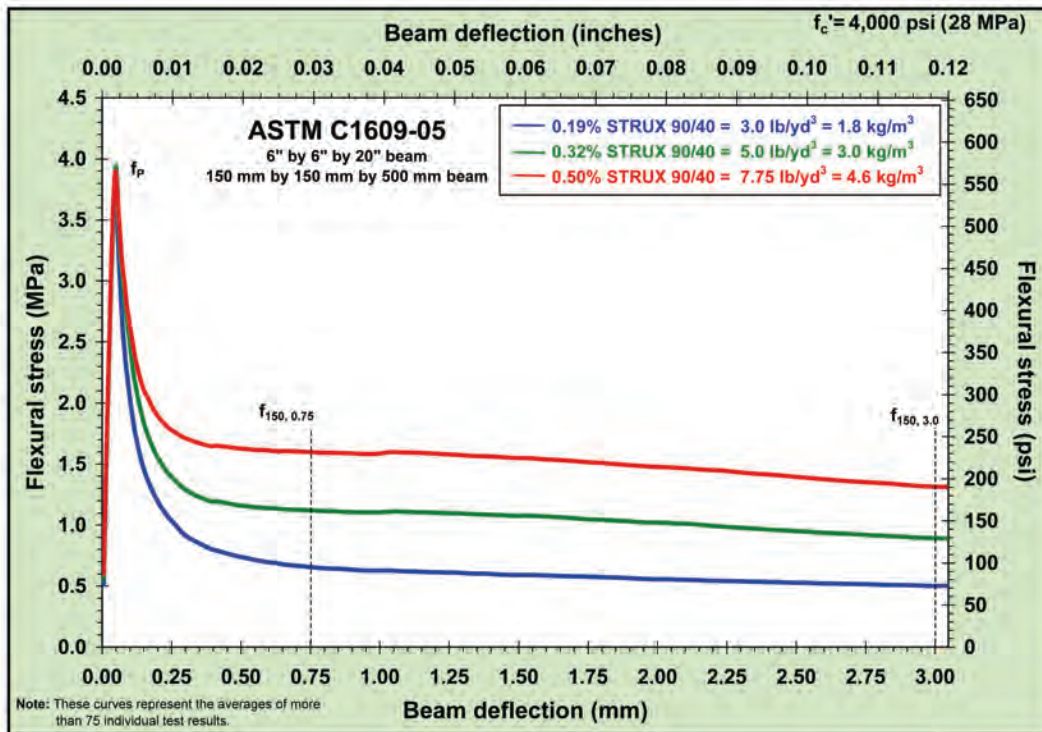

www.graceconstruction.com

North American Customer Service: 1-877-4AD-MIX1 (1-877-423-6491)

STRUX and ADVA are registered trademarks and Concrete-Ready is a trademark of W. R. Grace & Co.—Conn.

We hope the information here will be helpful. It is based on data and knowledge considered to be true and accurate and is offered for the users' consideration, investigation and verification, but we do not warrant the results to be obtained. Please read all statements, recommendations or suggestions in conjunction with our conditions of sale, which apply to all goods supplied by us. No statement, recommendation or suggestion is intended for any use which would infringe any patent or copyright. W. R. Grace & Co.—Conn., 62 Whittemore Avenue, Cambridge, MA 02140. In Canada, Grace Canada, Inc., 294 Clements Road, West, Ajax, Ontario, Canada L1S 3C6.

This product is covered by U.S. Patent Nos.: 6,569,525; 6,569,526; 6,758,897; 6,863,969.
STRUX-5M Printed in U.S.A. 11/07 FA/LI/1M

Copyright 2007. W. R. Grace & Co.—Conn.

GRACE